

LN-9 IDLE MIND SOLUTIONS

1. Given: $E_a = 315 \text{ kJ/mole}$
 $D_0 = 1.70 \text{ cm}^2/\text{s}$

At what T will D be $5 \times 10^{-11} \text{ cm}^2/\text{s}$?

$$D = D_0 \exp(-E_a/RT)$$

$$5 \times 10^{-11} = 1.70 \exp\frac{-315,000}{8.3 T}$$

$$\ln \frac{5 \times 10^{-11}}{1.7} = -\frac{E_a}{RT}$$

$$T = \frac{E_a}{24.2 \times R}$$

$$T = 1563\text{K} = 1290^\circ\text{C}$$

2. D for Li into Si is given as:
 $10^{-5} \text{ cm}^2/\text{s}$ at 1100°C (1373K)
 $10^{-6} \text{ cm}^2/\text{s}$ at 692°C (965K)

Thus:

$$10^{-5} = D_0 e^{-E_a/RT_1}$$

$$10^{-6} = D_0 e^{-E_a/RT_2}$$

$$10 = e^{-\frac{E_a}{R}\left(\frac{1}{T_1} - \frac{1}{T_2}\right)} \quad 2.3 = -\frac{E_a}{R}\left(\frac{1}{T_1} - \frac{1}{T_2}\right)$$

$$E_a = -\frac{2.3 \times R}{\frac{1}{T_1} - \frac{1}{T_2}} = 62 \text{ kJ/mole}$$

$$10^{-5} = D_0 e^{-E_a/RT}$$

$$D_0 = 10^{-5} \times e^{E_a/RT} = 2.3 \times 10^{-3}$$

3. Since electrons do not electrostatically interact with the electron shells of the atoms, they encounter “virtually empty space” and accordingly the diffusion constant for neutrons must be expected to be **significantly larger than even the diffusion constants of liquids**.

$$4. \frac{c}{c_0} = 0.5 = \operatorname{erfc} \frac{x}{2\sqrt{Dt}} = \operatorname{erf} \frac{x}{2\sqrt{Dt}}$$

From the tables we find $\frac{x}{2\sqrt{Dt}} = 0.48$

$$t = \frac{x^2}{(0.96)^2 \times D} = \frac{9 \times 10^{-8}}{0.92 \times 8 \times 10^{-12}}$$

$$t = 12228 \text{ sec} = 3.4 \text{ hours}$$

5. The diffusion profile in Fe is given by $\frac{c}{c_0} = \operatorname{erfc} \frac{x}{2\sqrt{Dt}}$ with $c/c_0 = \text{const}$.

Correspondingly: $\frac{x}{2\sqrt{Dt}} = \text{const}$

$$\text{or } \frac{x}{\sqrt{t}} = K \text{ and } \frac{x^2}{t} = K'$$


This constant can be determined with the information given:

$$K' = \frac{(0.04)^2}{10} = 1.6 \times 10^{-4} \text{ cm}^2/\text{h}$$

The time for diffusion to a depth y (0.08) is then given as:

$$t = \frac{y^2}{K'} = \frac{(0.08)^2}{1.6 \times 10^{-4}} = 40 \text{ hours}$$

6. First a clarification: What is the origin of the indicated composition gradient across grains of a Cu-Ni alloy? It is explained by a look at the phase diagram. Melt of composition C_L freezes into grains of steadily increasing radius; obviously the growth stops when all the melt around this grain has solidified (onto this and other grains).

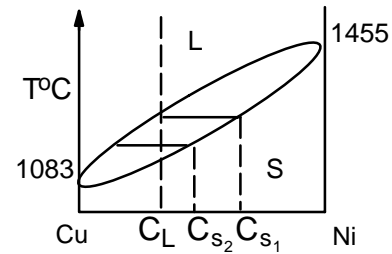

With increasing radius the freezing alloy first has the composition C_{S_1} , which steadily increases to C_{S_2} and even higher (why?). This phenomenon is referred to as “coring”.

When we consider diffusive effects, we like to talk about the “effective diffusion distance”: the distance over which the original surface concentration has decreased to 50% of its value ($c = c_0/2$). Thus:

$$\frac{c}{c_0} = 0.5 = \operatorname{erfc} \frac{x}{2\sqrt{Dt}}$$

The answer to the question:

$$D = D_0 e^{-E_a/RT} = 2.7 e^{-\frac{(235 \times 10^3)}{(8.314 \times 1373)}} = 3.1 \times 10^{-9} \text{ cm}^2/\text{s}$$

$$0.5 = \operatorname{erfc} \frac{x}{2\sqrt{Dt}} \cong \frac{x}{2\sqrt{Dt}}$$

$$x = \sqrt{Dt}$$

$$t = \frac{x^2}{D} \quad (x = \text{radius of the grain} - 0.005 \text{ cm})$$

$$t = 8065 \text{ sec} = 2.2 \text{ hours}$$

7. $T = 1600\text{K}$
 $D = 8 \times 10^{-12} \text{ cm}^2/\text{s}$

$$\frac{c_2 - c(x, t)}{c_2} = \text{erf}\left(\frac{x}{2\sqrt{Dt}}\right) \quad \text{want } c(x, t) = 1/2(c_2)$$

$$\frac{c_2 - \frac{c_2}{2}}{c_2} = \frac{1}{2} = \text{erf}\left(\frac{x}{2\sqrt{Dt}}\right)$$

Interpolating from Table II:

we find for $\text{erf}(Z) = 0.5000$, $Z = 0.4772$

$$\frac{x}{2\sqrt{Dt}} = 0.4772$$


$$x^2 = 0.4772^2 2^2 Dt = 0.911 x Dt$$

$$t = \frac{(3 \times 10^{-4})^2}{0.911 (8 \times 10^{-12})}$$

$$t = 1.23 \times 10^4 \text{ sec} = \boxed{3.43 \text{ hrs}}$$

8. To solve this type of problem, it is best to sketch the conditions:

$$\frac{C}{C_0} = 1 - \operatorname{erf} \frac{x}{2\sqrt{Dt}}$$

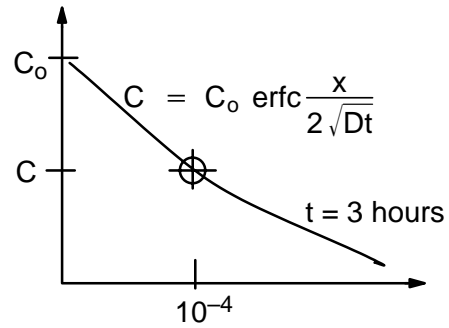

$$(a) \quad C = 10^{18} \left(1 - \operatorname{erf} \frac{10^{-4}}{2\sqrt{7 \times 10^{-13} \times 3 \times 3600}} \right)$$

$$C = 10^{18} (1 - \operatorname{erf} 0.575)$$

$$C = 10^{18} (1 - 0.58)$$

$$C = 4.2 \times 10^{17} / \text{cm}^3$$

$$(b) \quad C = 10^{18} [1 - \operatorname{erf} (0.575 \times 3)]$$

$$C = 10^{18} (1 - 0.98)$$

$$C = 2 \times 10^{16} / \text{cm}^3$$

$$9. \quad \frac{C}{C_0} = \left(1 - \operatorname{erf} \frac{x}{2\sqrt{Dt}} \right)$$

$$0.3 = 1 - \operatorname{erf} \frac{x}{2\sqrt{Dt}}$$

$$0.7 = \operatorname{erf} \frac{x}{2\sqrt{Dt}}$$

From the tables we have: $\frac{x}{2\sqrt{Dt}} = 0.74$

$$\sqrt{Dt} = \frac{x}{1.48}$$

$$t = \frac{(8 \times 10^{-4})^2}{1.48^2 \times 8 \times 10^{-12}}$$

$t = 36529 \text{ s} = 10.1 \text{ hours}$
--

$$10. \quad 0.5 = \operatorname{erf} \frac{x}{2\sqrt{Dt}}$$

$$\frac{x}{2\sqrt{Dt}} = 0.48$$

$$\sqrt{Dt} = \frac{x}{0.96}$$

$$t = \frac{x^2}{0.96^2 \times 8 \times 10^{-12}}$$

$t = 37.7 \text{ hours}$

$$11. \quad C = C_o \operatorname{erfc} \frac{x}{2\sqrt{Dt}}$$

$$0.35 C_o = C_o \operatorname{erfc} \frac{x}{2\sqrt{Dt}}$$

$$0.35 = \operatorname{erfc} \frac{x}{2\sqrt{Dt}}$$

$$0.35 = 1 - \operatorname{erf} \frac{x}{2\sqrt{Dt}}$$

$$0.65 = \operatorname{erf} \frac{x}{2\sqrt{Dt}} \quad \text{From the table: } \frac{x}{2\sqrt{Dt}} = 0.65$$

$$\sqrt{Dt} = \frac{x}{1.3}$$

$$t = \frac{(0.01)^2}{1.3^2 \times 10^{-10}}$$

$$t = 164 \text{ hours}$$

12. Carburization is a diffusion controlled process; therefore:

$$X = k\sqrt{t}$$

$$X^2 = kt \quad k = \frac{X^2}{t} = \frac{(0.04)^2}{10} = 1.6 \times 10^{-4} \text{ cm}^2/\text{h}$$

$$0.08^2 = 1.6 \times 10^{-4} (t_x)$$

$$t_x = 40 \text{ hours}$$

$$13. \frac{C}{C_0} = 0.2 = \operatorname{erfc} \frac{x}{2\sqrt{Dt}}$$

$$0.8 = \operatorname{erf} \frac{x}{2\sqrt{Dt}}$$

$$\text{From the table: } \frac{x}{2\sqrt{Dt}} = 0.91$$

$$t = \frac{0.02^2}{1.82^2 \times D} \quad D = 0.47 e^{-\frac{332 \times 10^3}{8.314 \times 1273}}$$

$$t = 1.1 \times 10^{10} \text{ s} \quad D = 1.1 \times 10^{-14} \text{ cm}^2/\text{s}$$

$$t = 348 \text{ years}$$

$$14. \frac{C_x}{C_2} = \operatorname{erfc} \frac{x}{2\sqrt{Dt_x}} = 1 - \operatorname{erf} \frac{x}{2\sqrt{Dt_x}}$$

To solve this problem you need to know $D_{1375\text{K}}$ which can be read from the accompanying graph as $D_{1375\text{K}} = 8 \times 10^{-13} \text{ cm}^2/\text{s}^{-1}$.

$$(a) \quad c_x = c_0 \left(1 - \operatorname{erf} \frac{1 \times 10^{-4}}{2\sqrt{3 \times 3600 \times 8 \times 10^{-13}}} \right) = c_0(1 - \operatorname{erf} 0.538)$$

$$\text{From LN9-12 we have } = c_0(1 - 0.553)$$

$$c_x = 10^{18}(1 - 0.553)$$


$$c_x = 4.5 \times 10^{17} \text{ at/cm}^3$$

$$(b) \quad c_x = c_0 \left(1 - \operatorname{erf} \frac{3 \times 10^{-4}}{2\sqrt{3 \times 3600 \times 8 \times 10^{-13}}} \right)$$

$$= c_0(1 - \operatorname{erf} 1.62)$$

$$= c_0(1 - 0.978) = 2.2 \times 10^{16} \text{ at/cm}^3$$

15. If a metal oxidizes according to a linear rate law, it means the thickness (x) of the oxidation product (rust) is proportional to time ($x = kt$).

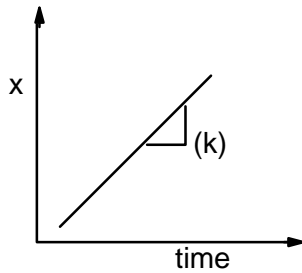


For such a process, $(dx)/(dt) = k = \text{const}$. This is typically the case if the oxidation product is “non-coherent” and oxygen has direct access to the metal surface.

If aluminum is added, the aluminum will form a coherent film of Al_2O_3 through which oxygen cannot readily diffuse.

Further oxidation is therefore very slow. This behavior can be expressed as

$$x = k \log (at + b)$$

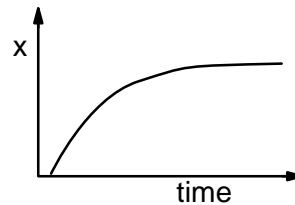

Hence the oxidation follows a logarithmic rate law.

16. A solution to Fick's 1st law for the given boundary conditions was presented in class:

$$\frac{c}{c_0} = 1 - \operatorname{erf} \frac{x}{2\sqrt{Dt}} \quad \operatorname{erf} \frac{x}{2\sqrt{Dt}} = 1 - 0.018 = 0.982$$

From the error function tables we find that the argument which yields an error function value of 0.982 is given by 1.67. This means:

$$\frac{0.002}{2\sqrt{Dt}} = \frac{0.001}{\sqrt{Dt}} = 1.67 \quad ; \quad D = D_0 \cdot e^{\frac{-286 \cdot 10^5}{8.314 \cdot 1253}} = 6.45 \cdot 10^{-13} \frac{\text{cm}^2}{\text{sec}}$$

$$t = \frac{0.001^2}{1.67^2 \cdot 6.45 \cdot 10^{-13}} = 5.56 \cdot 10^5 \text{ sec} = 6.4 \text{ days}$$

